

Modification of multi-walled carbon nanotube by p-amino acetanilide for extraction of buspirone drug

ShirinReshad^a, Zahra Azizi^{b*}, ElhamMoniry^c

^{a,b} *Department of Chemistry, Karaj Branch, Islamic Azad University, Karaj, Iran*

^c *Department of Chemistry, Varamin Branch, Islamic Azad University, Varamin, Iran*

*Corresponding author: Zahra Azizi (E-mail: Zahra Azizi@yahoo.com)

Abstract

The improvement of medication techniques that causes the reduction of toxicity and enhancement of drug effectiveness enjoys a special significance. Hence, attempts have been made in this research to use factored-in carbon nanotube for measurement and determination of the dose of anti-anxiety disorder drugs in human body's liquids. In the first place, in order to possess more active sites, the multi-walled carbon nanotube was factored-in by cyanuric chloride. Then p- amino acetanilide was placed on the absorbent, as a ligand that has an exclusive suitable coaction with the buspirone drug. In order to confirm the synthesized nanostructure, different techniques, including Infrared Spectrometry (FT-IR), TGA, SEM, EDAX were used and the results were analyzed. In order to determine the optimum conditions, the absorption of the drug under pH conditions and optimum time was studied. Finally, under optimum conditions, the absorption of the drug in blood plasma and urine were carried out by High Performance Liquid Chromatography (HPLC).

Keywords: Carbon nanotube, Functionalized, P-amino acetanilide, Buspirone, HPLC, Drug

1. Introduction

Nanotechnology is a new approach in most fields, and what it plays a role in comprehensiveness epidemic is high surface area to volume ratio of materials.

This is one of the most important properties of materials produced in nanoscale Carbon compound have been taken an important role in this field [1].

After the discovery of the third allotropic form of carbon fullerene in 1991, Sumio Iijima identified a new structural form of this allotrope, the cylindrical fullerene and named them as carbon nanotubes (CNTs) [2].

There are two groups of carbon nanotubes: multi-walled carbon nanotubes (MWCNT) and single-walled carbon nanotubes. Carbon nanotubes (CNTs) have drawn considerable attention for many years due to their excellent electrical, mechanical, thermal, and optical properties. The unique structure and excellent properties allow carbon nanotubes to be suitable for many applications [3-5]. They can be used in many fields such as nanoelectronic devices, sensor, energy storage, nanocomposite (NC) materials and drug delivery [6]. Many research groups have reported different functional reactions on carbon nanotubes. According to studies, these reactions are divided into two categories which are non-covalent functionalization (hydrophobic interaction between molecules and nanotubes; π - π interactions between the non-resident electrons. electrostatic forces between non-resident electrons of nanotubes with positive charge of surfactant etc.) and covalent functionalization (direct connection of the functional groups to

surface; direct covalent binding of carboxylic acid groups). Covalent bonds between functional groups with carbon nanotubes are very promising, since they create a very sturdy connection. According to the reported results, carbon nanotubes containing mixture of H_2SO_4 / H_2O_2 , H_2SO_4 / HNO_3 , H_2O_2 / HNO_3 , $KMnO_4$, or using of superoxide at room temperature or heat Results in opening the closed-end of materials, and they are functionalized at an end and on the surface [7-11]. In this article, carboxylated-multiwalled carbon nanotubes were functionalized with cyanuric chloride then modified by p-amino acetanilide. carboxylated-multiwalled carbon nanotubes functionalized were used to measurement and determine the amount of buspirone drug in human body fluids. Buspirone with chemical name 8-[4-(4-pyrimidin-2-ylpiperazin-1-yl)butyl]-8-azaspiro[4.5]decane-7,9-dione; hydrochloride is an anxiolytic agent and serotonin receptor agonist belonging to the azaspirodecanedione class of compounds (Fig. 1).

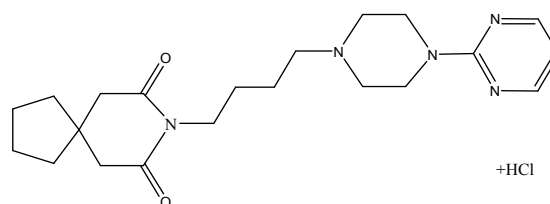


Fig. 1. Structures of Buspirone

Multiwalled carbon nanotubes modified was characterized by Fourier transform infrared spectroscopy (FT-IR), thermal gravimetric analysis (TGA), scanning electron microscope (SEM) and energy dispersive spectroscopy (EDAX) were used to confirm the nanostructure synthesized. In order to determination of the optimum conditions, the effects of varying parameters such as pH, contact

2. Experimental

2.1. Instruments

Infrared spectra were recorded on Fourier transform infrared spectroscopy (Spectrum100, PerkinElmer, Baesweiler, Germany). Thermogravimetric analysis was carried out using a TGA/SPTA851 (Mettler Toledo, Germany). The scanning electron microscopy (SEM) micrographs were obtained on a MIRA3 TESCAN of RMRC (USA) scanning electron microscopy. Elemental analysis was carried out on a Thermo-Finnigan model Flash EA elemental analyzer.

2.2. Reagents and solutions

MWCNT-COOH (purity >95 wt.%, inner diameter of 3–5 nm, outer diameter of 15–20 nm, length and ~50 μm carboxyl content of 1.56 wt.%), was obtained from US Research Nanomaterials, Houston,

time, concentration and desorption were examined in various solutions. Later on, through applying the optimum condition, efficiency of the drug adsorption and desorption were evaluated in plasma. Spectroscopy ultraviolet (UV) and high performance liquid chromatography (HPLC) were used for determining of drug adsorption value and verification of drug desorption in plasma respectively.

Texas, USA. Buspirone was purchased from Tehran drug co, Iran. In addition, cyanuric chloride, p- amino acetanilide, 1,4-dioxane, methanol, Potassium dihydrogen phosphate, Xylene, acetic acid and all the inorganic acid and salt were products of Merck (Darmstadt, Germany).

The stock solution of Buspirone was prepared in water (500 mg L^{-1}). All solutions were made by stock solution and their pH was adjusted by acetate buffer. For preparing the buffer used in the mobile phase, 10mM of buffer phosphate solution (KH_2PO_4) was solved in the pure distilled water and then the solution's pH was adjusted 5.0 ± 0.01 using the concentrated phosphoric acid solution. For preparing a standard sample of 1000 $\mu\text{g mL}^{-1}$ of Buspirone drug, 0.01g of this drug was weighted and reached a desired volume using H_2O in a 10-ml volumetric flask. For making more dilute samples, including 1, 2, 5, 10, 15, 20, 25 and 30 $\mu\text{g mL}^{-1}$ (8

points for calibration), a certain amount of the reference solution reached a 10-ml volume.

2.3 Preparation of MWCNT- COOH/ P-amino acetanilide

First, a sample of acetylated carboxylic carbon nanotube (CNT-COOH) was purchased and forwarded for FT-IR, TGA tests, observed in Fig. 2, 5 respectively. 1.5 g of cyanuric chloride was solved by a 25:25 mixture of xylene/dioxane in a beaker at 25°C for 1h through mixing (250rpm). Then, 2g of Carboxylated carbon nanotube was added to the beakers solution. The reaction continued at 25°C for 24h (250rpm). The resulted compound was smoothed by nanopaper and washed by 20mL of petroleum ether several times in order to remove pollutants. Then, it was dried under the temperature of 40°C for 24h in oven and consequently a sample of the resulted powder was forwarded for IR test, observed in Fig.3.

For the synthesis of the final carbon nanotubes functionalized by P- amino acetanilide, 100 mL of sodium acetate buffer (0.01M) was poured into an reflux system and 1g of P- amino acetanilide was added in order to be solved under the temperature of 65-70°C through mixing (250rpm) for 2h. Finally, the compound resulted from the previous step (CNT-Group) was added to the solution and

reflux was continued for 12 hours. The resulted powder was washed by the deionized water and 0.1 molar sodium chloride and dried at the temperature of 40°C for 24h in oven. A sample of Nanoadsorbent was forwarded for FT-IR, TGA and SEM tests, observed in Fig. 4, 6 and 7, respectively

2.4. Chromatographic conditions

In order to analyze the drug, HPLC apparatus equipped with a UV-VIS detector and the column C18 (250mm × 4.6 mm id, 5µm) was used. The Buffer used in the solution system 10mM has been of the phosphate buffer (KH₂PO₄) which was arranged by the phosphoric acid solution with pH=7.5. The mobile phase consisted of phosphate buffer solution of 10mM with pH=3 and Acetonitrile in the ratio (40:60) was used. Flow rate was 1 ml / min and the injection volume of 20 micro-liters well as the column temperature was set to 35 degrees Celsius. The Wavelength set for the detector equals to 238nm.

2.5. Sorption & Recovery of Buspirone Drug

Solutions of Buspirone drug with concentrations of 1 and 20 $\mu\text{g mL}^{-1}$ (concentration 20 for determining optimum parameters and concentration 1 for sorption of drug in plasma) and pH=3 (adjustment of pH by buffer) were prepared in a 10-ml volumetric flask and 2 mL of them was added to the microtube. Then, 0.05g of the adsorbent was added to microtubes containing solutions in order to be mixed for 15 minutes. It led to the adsorption of *Buspirone* drug on the adsorbent. After the end of mixing, samples were centrifuged and supernatant was filtered by the syringe tip filter and finally injected to HPLC for determining the volume. Then, the drug adsorbed on the adsorbent was recovered by the optimum desorption solvent. HPLC was used for determining the concentration. After the determination and adoption of optimum conditions of parameters, the sorption and recovery percentage of drug (with the concentration of 1 $\mu\text{g mL}^{-1}$) relative to a standard similar to its environment was quantified by HPLC.

2.6. Adsorption isotherms/ kinetics

The adsorption capacity was measured in batch experiments then the adsorption

model was determined. Isotherm studies were performed by adding 0.02 g of modified MWCNTs a series of microtubes filled with 3 mL of diluted solutions Buspirone (5, 10, 15, 20, 30, 50 $\mu\text{g mL}^{-1}$) in acetate buffer, pH=5. The micro-tubes were shaken for 15 min. after that samples were centrifuged at 8000 rpm for 5 min.

3. Results and discussion

3.1. Characterization of structures

3.1.1. Review of Spectrum (FT-IR)

In order to verify the structure of samples in each step, their IR spectrum was reviewed. Results of FT-IR, MWCNT-COOH, MWCNT-COOH/ $\text{C}_3\text{Cl}_3\text{N}_3$ and MWCNT-COOH/P-amino acetanilide are observed in Fig. 2, 3 and 4, respectively.

In figure 2, the peak observed in the area 1634 cm^{-1} is related to carboxyl C=O existing in -COOH. Furthermore, the wide peak band observed in the area 3400 cm^{-1} is related to OH stretching vibration.

In a spectrum provided in figure 3 and 4, the peak observed in the area 1714 cm^{-1} is related to C=O carboxyl group existing. In addition, stretching vibrations between carbon and chlorine C-Cl and C-H Stretching vibration was observed.

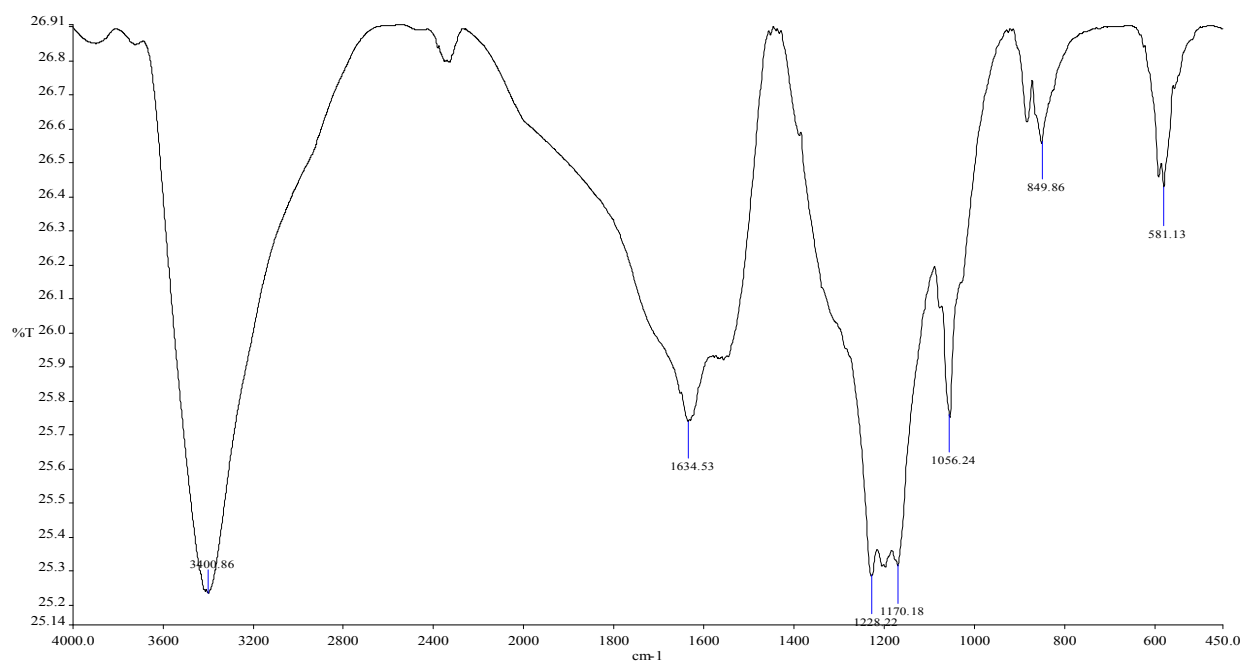


Fig.2 : FT-IR spectrum of the carboxylated multi-walled carbon nanotube

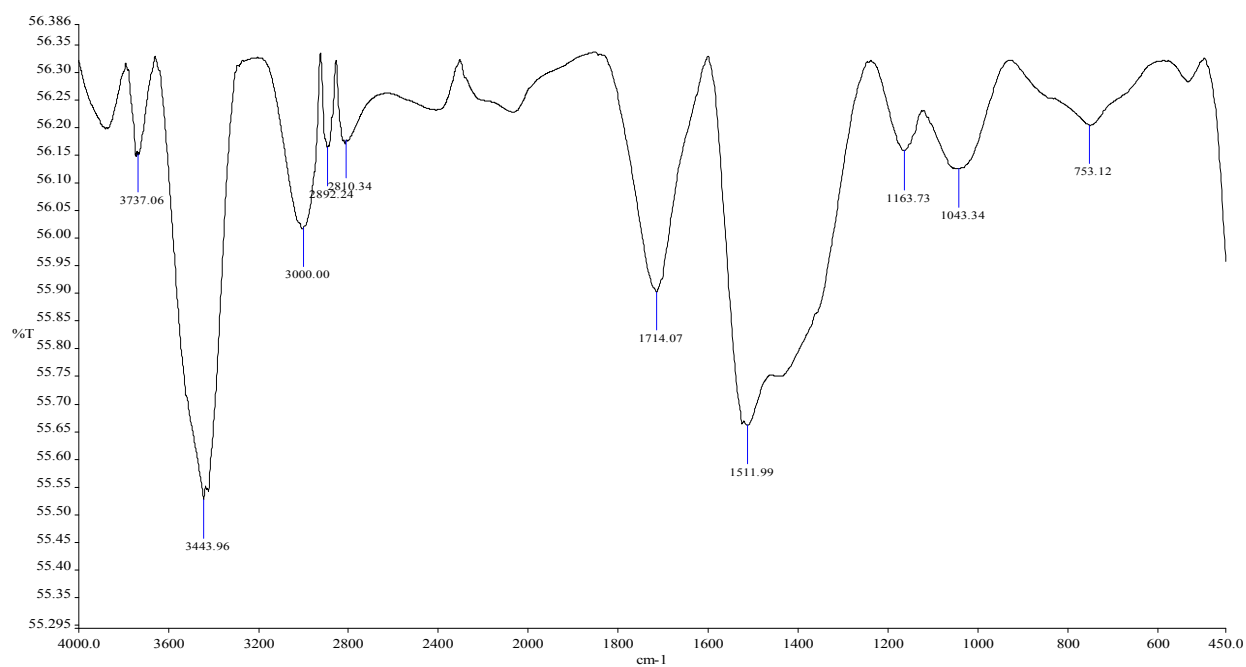


Fig.3 : FT-IR spectrum of the multi-walled carbon nanotube functionalized by cyanuric chloride

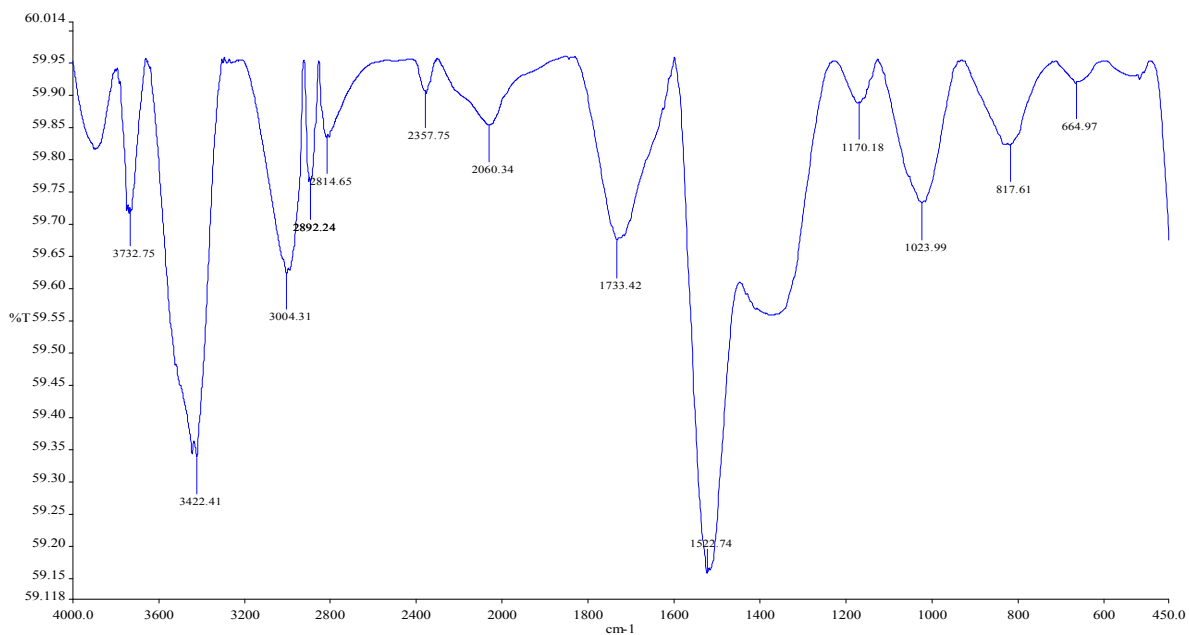


Fig.4 : FT-IR spectrum of the multi-walled carbon nanotube modified by P- amino acetanilide

3.1. 2. Review of TGA

According to the spectrum provided in Fig.5, the initial nanotube has a stable structure which maintains its structural skeleton to the temperature of 600°C. Of

course, there are impurities in the compound which are analyzed. On the other hand, Fig.6. shows a structure with a modified surface, indicating a reduction in the structure's resistance at high temperatures.

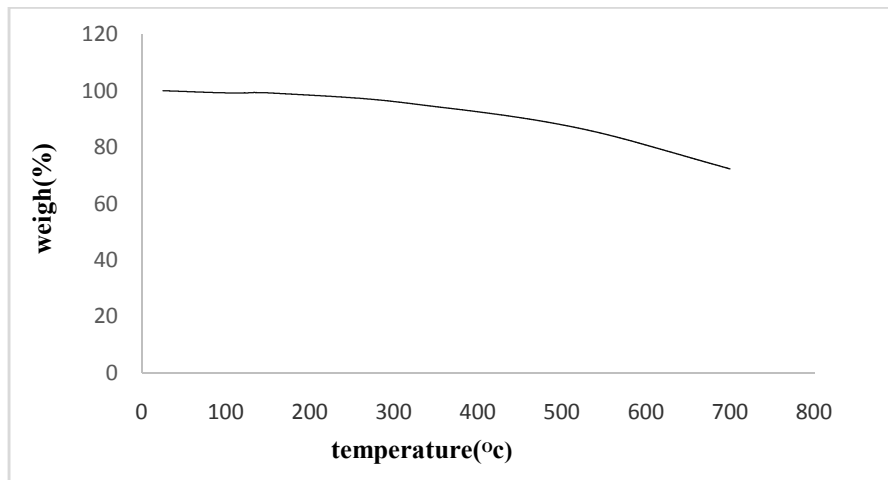


Fig 5.Results obtained from TGA;Thecarboxylated multi-walled carbon nanotube (MWCNT-COOH)

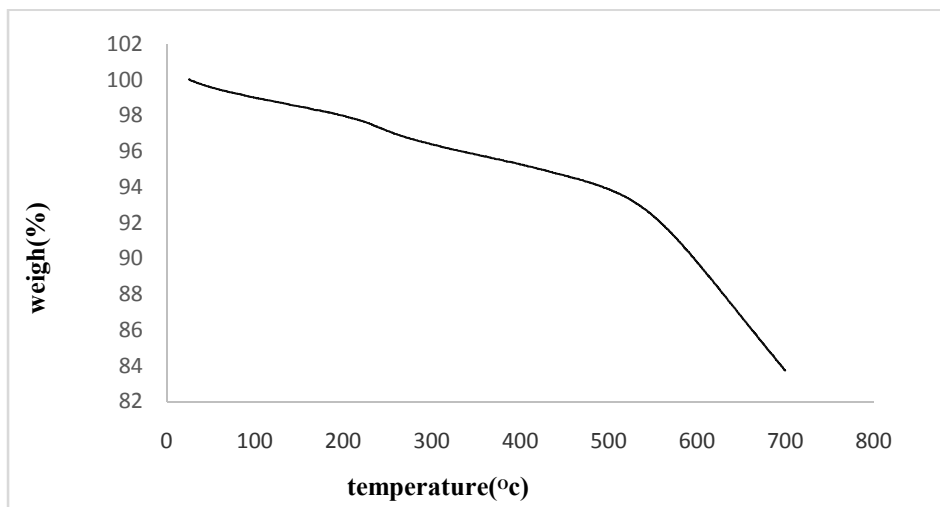


Fig 6. Results obtained from TGA; The final functionalized multi-walled carbon nanotube

3.1. 3. SEM microscopy

Fig. 7. is the SEM image in a 200 nm scale of the initial carboxylated carbon nanotube .The bumps surface and increase in the diameter is due to the several

chemical reactions and the covalent bond (bonding) of the functional groups on the wall of nanotubes. It verifies the modification of the nanostructure's surface.

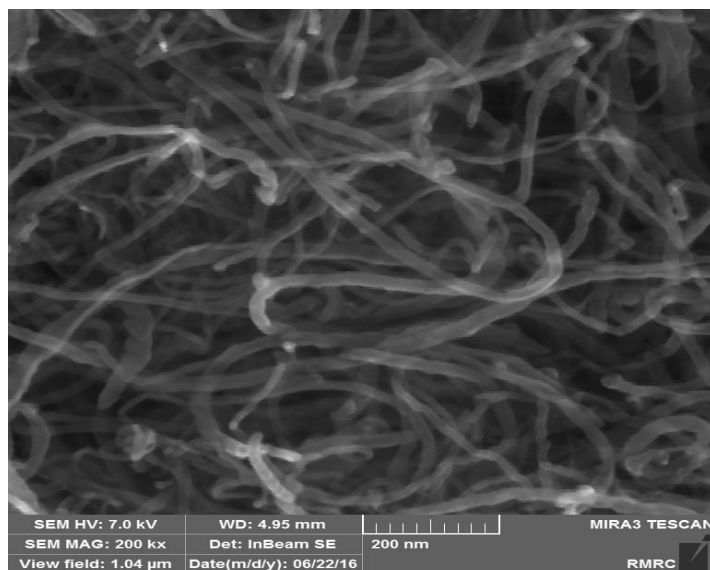


Fig. 7. FESEM image of the final functionalized multi-walled carbon nanotube (MWCNT-P-amino acetanilide).

3.1. 4. Assessment of functionalization by EDAX

Further evidence for the multifunctionalization of pristine

MWCNTs is provided by energy dispersion spectroscopic (EDAX) analysis. The EDAX spectrum of MWCNTs-COOH (Fig. 8) and MWCNTs-P-amino acetanilide (Fig. 9) is shown in table 1.

Table 1. Result edax of MWCNTs-COOH and MWCNTs-P-amino acetanilide

MWCNTs-COOH	Element	C	O	Cl	S	Ca
	Wt%	92.42	6.87	0.14	0.31	0.26
MWCNTs- P- amino acetanilide	Element	C	O	Cl	S	Ca
	Wt%	90.62	8.71	0.41	0.16	0.09

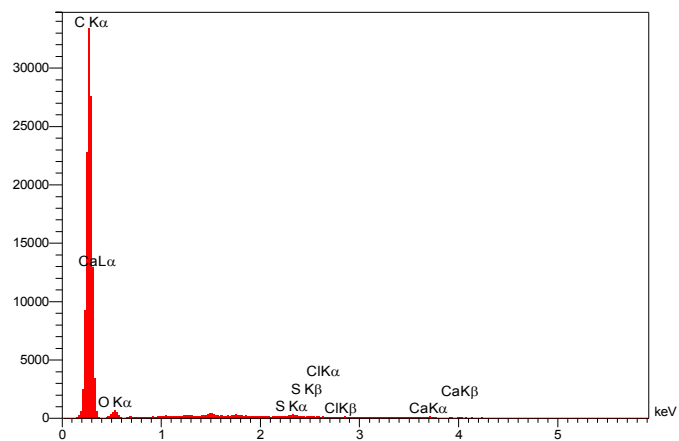


Fig. 8. Result edaxof MWCNTs-COOH

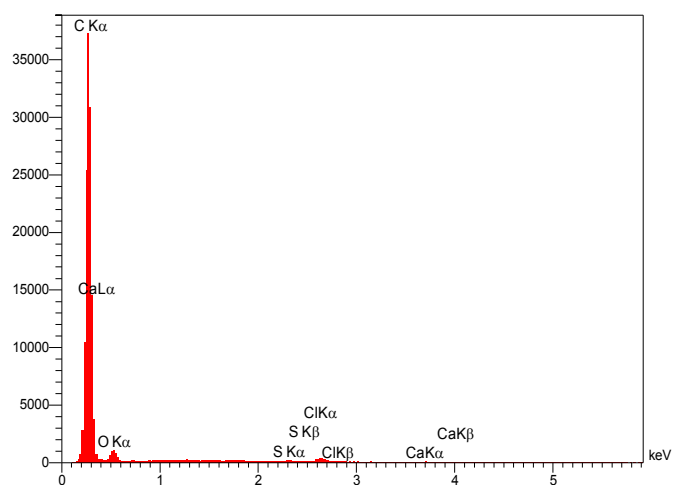


Fig. 9. Result edaxof MWCNTs-COOH and MWCNTs- P- amino acetanilide

3.2. Determination of Optimum pH & Mixing time

First, the maximum wavelength of Buspirone drug was determined (238 nm). Then, in the maximum wavelength, the drug's linear range is drawn between 1 and 30 $\mu\text{g mL}^{-1}$ and the computation of drug's concentration in reviewing parameters is studied in this range. The method's validation parameters are listed in table 2. The percentage of the drug adsorbed with the concentration of 20 $\mu\text{g mL}^{-1}$ in

different pH (3 - 8) was studied by HPLC which the best result of sorption was obtained in pH = 8. Its experimental results are shown in Fig 10. Then, by adjusting pH = 8 in the solution as the optimum pH, the optimum time was determined in the same concentrations of the drug (20 $\mu\text{g mL}^{-1}$). Given Fig. 11, the maximum sorption were obtained in 20 min.

Table 2. Validation parameters for standard solutions of Buspirone drug.

Line equation	Correlation coefficient (R^2)	Linear range	RSD% (experimental)	LOD (ng mL^{-1})	LOQ (ng mL^{-1})
$y=0.0534x + 0.0361$	0.995	1-30	0.97	13	43

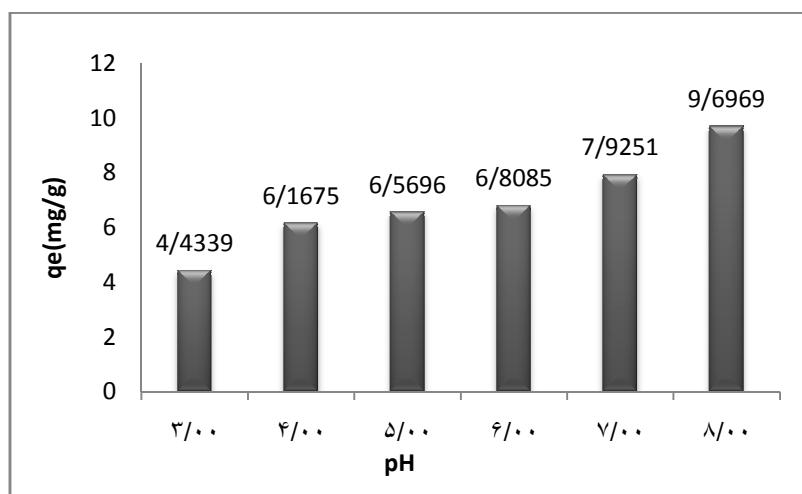


Fig 10. The effect of pH on the sorption of Buspirone drug by the Nanoadsorbent

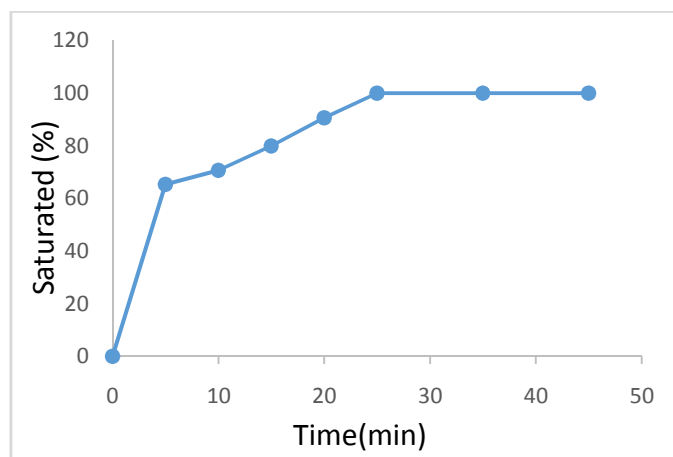


Fig 11. The effect of time on the sorption of Buspirone drug by the Nanoadsorbent

3.4. HPLC Results

After the determination of optimum conditions of sorption and recovery of Buspirone drug by the functionalized carbon nanotube, a solution containing the drug was prepared in the blood plasma and placed near the Nanoadsorbent. Then, the

drug adsorbed by the acetonitrile solvent on the Nanoadsorbent was recovered and injected to the device. Based on the results of spectrums provided in Fig. 12 and 13, the sorption percentages of plasma and urine result shoes in table 3 and 4.

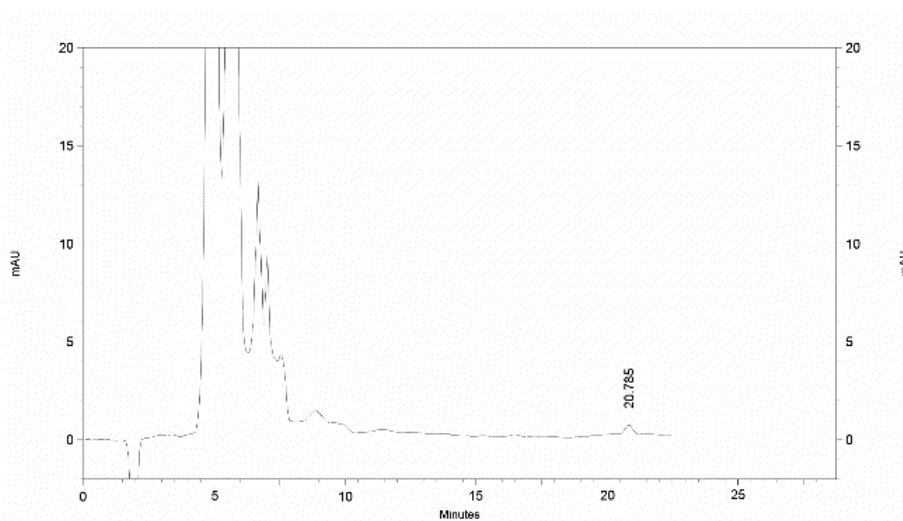


Fig 12. HPLC results of sorption of drug in the blood plasma

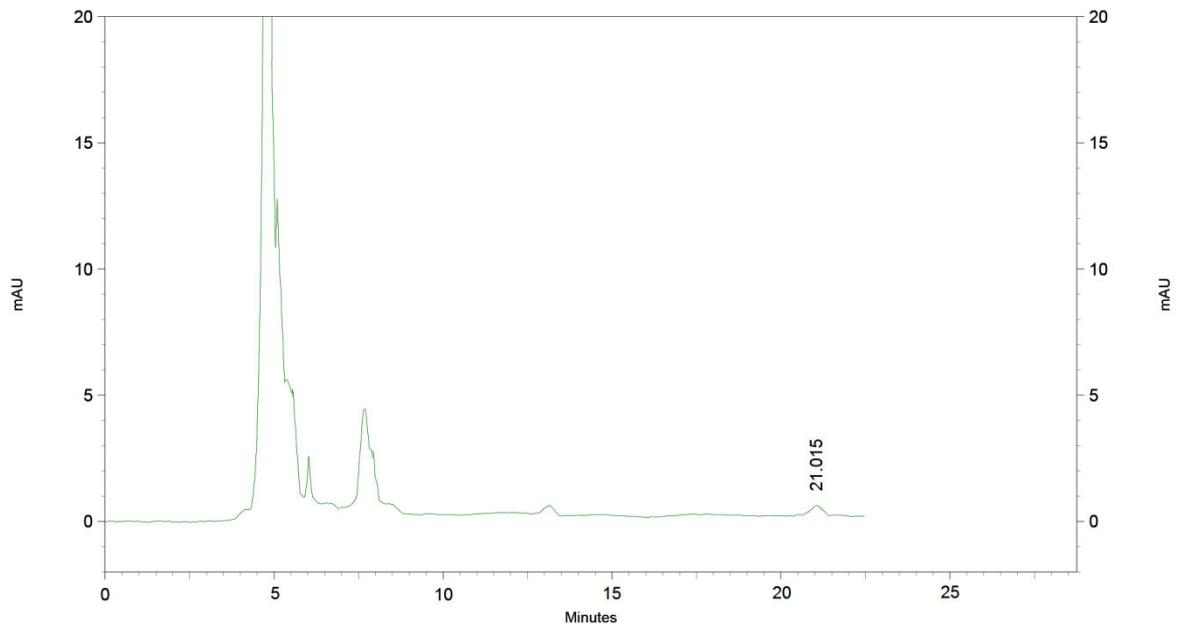


Fig 13. HPLC results of sorption of drug in the urin

Table 3. The sorption percentages of drug in plasma by HPLC

Name	Sorption Of Drug
SampleRetesion Time	21.015
SampelArea	1021
StandardRetesion Time	20.971
Area Standard	9411
C(mg/l)	0.108
Adsorbed%	89.200

Table 4. The sorption percentages of drugin urinby HPLC

Name	Sorption Of Drug
SampleRetesion Time	20.785
SampelArea	1123
StandardRetesion Time	20.971
Area Standard	9411
C(mg/l)	0.119
Adsorbed%	88.100

4. Conclusion

Chemical reformation and solubility of Carbon Nanotubes made a vast criteria for research in this field. Many functionalization reactions by covalent and non-covalent mechanisms have been reported for Carbon Nanotubes by many researchers. In this research adding functional group by covalent mechanism in multi membrane Nanotubes in order to make nanostructures capable of reacting with soluted drug in Plasma was done. This would be an approach to extract, preconcentrate and measure drugs

from Plasma. In general, by functionalizing the multi-walled carbon nanotube and studying the effect of different factors on the sorption of Buspirone drug on the adsorbent, the best absorption was obtained in pH=8 and 20min. Finally, by applying optimum conditions, the efficiency of adsorbent in the adsorption was evaluated in the plasma and urin. The maximum adsorption of drug was (89%) of drug were determined through HPLC with a low concentration. The maximum adsorption of drug was (88%) of drug were determined through HPLC with a low concentration.

Reference

- [1] Aliev,., Oh, J., Kozlov, M.E.,Kuznetsov, A.A., Fang, S., Fonseca, A.F.,Ovalle, R., Lima, M.D., Haque, M.H.,Gartstein, Y.N., Zhang, M., Zakhidov,A.A., and Baughman, R.H. (2009). Giantstroke,superelastic carbon nanotubeaerogel muscles, *Science*, 323, 1575.
- [2] S.Iijima,“Helical microtubules of graphitic carbon(1991)”*Nature*,vol. 354, no. 6348, pp. 56–58,.
- [3] A. M. A. Elhissi, W. Ahmed, I. Ul Hassan, V. R. Dhanak, and A.D’Emanuele (2012)“Carbon nanotubes in cancer therapy and drug delivery,” *Journal of Drug Delivery*, vol., Article ID 837327, 10 pages.
- [4] N. Dementev, R. Ronca, & E. Borguet. (2012) Oxygen-containing functionalities on the surface of multi-walledcarbon nanotubes quantitatively determined by fluorescent labeling, *Appl. Surf. Sci.* 258 10185– 10190.
- [5] Amelinckx, S., Bernaerts, D., Zhang, X.B.,VanTendeloo, G., and Van Landuyt, J.(1995) A structure model and growthmechanism for multishell carbonnanotubes. *Science*, 267, 1334.
- [6] Tahermansouri H, Biazar E (2013) Functionalization of carboxylated multi-wall carbon nanotubes with 3,5-diphenyl pyrazole and an investigation of their toxicity. *New Carbon Mater* 28:199–207.
- [7] Corona Giuseppe, EliaCaterina, Casetta Bruno. (2009). A liquid chromatography-tandem mass spectrometry method for the simultaneous determination of exemestane and its metabolite 17-dihydroexemestane in human plasma, *Journal of Mass Spectrometry*. 44, 920-928
- [8] Cenacchi V., Baratte S., Cicioni P., Frigerio E. (2000). LC–MS–MS determination of exemestane in human plasma with heated nebulizer interface following solid-phase extraction in the 96 well plate format, *J. Pharm. Biomed. Anal*22, 451-460.
- [9] Bhirde A., Patel V., (2009). GavardJ.Targeted killing of cancer cells in vivo and in vitro with EGF-directed carbon nanotube-based drug delivery, *ASC NANO*3, 307–316.
- [10] Fan, CW. Liu, YY.Hwu, C. (2009). Finite element simulation for estimating the mechanical properties of multi-walled carbon nanotubes. *ApplPhys A Mater*, 95, 819-31.
- [11] Yubing, W., Zafar I., Sanjay, V. M. (2005). Functionalization of carbon nanotubes with amines and enzymes.*Chemical Physics Letters*, 402, 96–101.